

[Click here to view linked References](#)

1
2
3 **Improved defect control and mechanical property variation in high pressure die casting of A380 alloy**
4 **by high shear melt conditioning**
5

6 *Y. Zhang, J. B. Patel, J. Lazaro-Nebreda, and Z. Fan

7 *Brunel Centre for Advanced Solidification Technology (BCAST), Brunel University London,*

8 *Kingston Lane, Uxbridge UB8 3PH, United Kingdom*

9 *(*Corresponding author: yijie.zhang@brunel.ac.uk)*
10
11
12
13

14 **Abstract:** To reduce the mechanical property variation of A380 alloy produced by high pressure die casting,
15 high shear melt conditioning (HSMC) technology was developed and applied to the melt prior to pouring
16 into shot sleeve. Experimental results show that with application of HSMC, the variation of elongation was
17 decreased from 21.8% to 13.9%, and yield strength variation was reduced from 5.5% to 3.6%. The improved
18 property variation is attributed to enhanced nucleation both in the shot sleeve and the die-cavity, and to the
19 improved distribution of porosity and secondary phases as a benefit of high shear induced grain refinement.
20 With application of high shear, large number of the Spinel phase ($MgAl_2O_4$) particles with double size
21 distribution in average diameter of 80nm and 300nm were formed. Due to the good orientation relationship
22 and small misfit between (α)-Al and $MgAl_2O_4$, the particles act as effective nuclei in shot sleeve and die
23 cavity respectively.
24
25
26
27
28
29

30 **INTRODUCTION**
31

32 A380 alloy has been widely used for production of automotive components by cold chamber high
33 pressure die casting (HPDC) process, due to its relatively good castability and mechanical properties, and
34 more importantly most of A380 ingots are usually produced from recycled materials [1–3]. This promotes
35 the use of A380 alloy and contributes to reducing CO₂ emissions when it comes to the lightweight in the
36 automotive industry. When the cold chamber HPDC process is chosen to produce the automotive components,
37 the mechanical properties of A380 alloy always have a large distribution range (named variation herein). In
38 other words, the properties are not stable or repeatable for each component produced. The reason for this
39 unpredictable variation is attributed to the typical solidification characteristics occurred in the HPDC process.
40 The HPDC process can be characterized in 3 steps regards to movement on melt. The first step is that the
41 melt is poured into the shot sleeve at a temperature of about 680°C, in which the shot sleeve is preheated by
42 a deliberate melt filling, or by a heating system. During this first step, solidification happens for the first time
43 in the shot sleeve which is known to be about 20% of the melt volume and produces coarse α -Al grains [4].
44 These coarse grains retain throughout the casting process and appear in the final products and are deemed to
45 cause the unpredictable variation of mechanical properties. The second step is that the melt is forced moving
46 forward by the plunger at about 0.2-0.3m/s until it approaches the inner gate of the mould. The third step is
47 that the melt is displaced very fast by the plunger at about 3-4m/s to complete the filling of die cavity and
48 refilling of the solidification shrinkage. The second solidification occurs in the die cavity and very fine α -Al
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 grains form due to a high pressure and high cooling rate of about 500-1000° C/s. From the solidification point
2 of view, the grain size is dominated by nucleation and growth. When the HPDC process is employed to
3 produce automotive components, the melt quality becomes the priority factor to control the solidification
4 process in comparison to other casting parameters.
5

6 The coarse α -Al grains formed in the shot sleeve are considered to be the main factor that affects the
7 mechanical properties stability. To minimize the existence of the coarse grains and then reduce mechanical
8 properties variation, various efforts have been taken, such as optimizing the filling process [5-6], increasing
9 shot sleeve temperature and pouring temperature [7]. Indeed, these methods can reduce the variation of
10 mechanical properties, but this improvement is achieved at the expense of shortening the lifetime of the shot
11 sleeve and die.
12

13 Grain refinement is proven that it is the best approach to obtain the fine uniform microstructure and
14 improve the yield strength and elongation simultaneously, and Al5Ti1B is the best grain refiner for Al alloys
15 currently [8–10]. During producing A380 alloy components, Al5Ti1B refiner was always added into melt as
16 a necessary casting procedure. In view of the specific solidification of HPDC and the characteristics of A380
17 alloy, the addition of Al5Ti1B refiner contributes limited improvement of mechanical properties variation.
18

19 Recently, physical refinement method by high shearing melt conditioning (HSMC) technique patented
20 by BCAST has been proved that it can refine most Mg and Al alloys [11–14]. The refinement mechanism is
21 that high shear can disperse the existing oxide films into fine particles as potential nuclei for Mg and
22 accelerate the formation of $MgAl_2O_4$ as effective nuclei for Al alloys.
23

24 In present study, the mechanical properties variation of A380 components produced via HPDC with
25 traditional melt processing, and with high shear melt conditioning prior to HPDC (MC-HPDC) was
26 investigated. The mechanisms of the influence of high shear both on shot sleeve solidification and die cavity
27 solidification are discussed.
28

29 **MATERIALS AND METHOD**

30 A380 alloy supplied by Norton was used as raw material for conducting HPDC processing, its
31 composition mainly contained 9.35%Si, 4.51%Cu, 1.51%Zn, 0.84%Fe, 0.32%Mn, 0.07%Mg and 0.065%Ti
32 (in wt.% percent). In the present study, clay-graphite crucible and electrical resistance furnace were used to
33 melt alloys, and two crucibles of 50Kg A380 ingots each were prepared for comparison of melt with and
34 without high shear melt conditioning. When the melt temperature reached 750° C, 30 minutes of holding
35 time was needed to uniform the composition distribution. Then, rotary degassing and high shearing melt
36 conditioning were employed in each crucible respectively. The parameters of rotary degassing were 350rpm
37 stirring speed for 8 minutes with Ar flow rate of 4L/min. High shear melt conditioning included two steps.
38 The first step was degassing with Ar flow rate of 0.2L/min and shearing 5 minutes at rotor speed of 1500rpm,
39 and the second step was only shearing at 1500rpm for 10 minutes to complete the melt conditioning treatment
40 without introducing Ar. After finishing melt treatment, the melt was poured into shot sleeve manually with
41 transfer ladle, and then melt was pushed into die cavity by plunge to obtain 8 tensile test samples with
42 6.35mm in diameter in extensometer part for each shot, in which the temperature of melt, shot sleeve and die
43 mold was 680° C, 180° C and 150° C respectively.
44


45 After 24 hours nature ageing, the samples were tested at as-cast state by Instron 5500 Universal
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 Electromechanical Testing System at an ambient temperature. The gauge length of the extensometer was 25
2 mm and the ramp rate for extension was 1mm/min. Specimens for microstructure analysis were cut from the
3 centre of the tensile sample bars with cross section perpendicular to tensile direction.
4

5 Pressure filtration melt cleanliness analyser (Prefil[®]-Footprinter) was also used after finishing melt
6 treatment (with and without HSMC) to collect the particles in the melt. Then, the samples were cut
7 perpendicular to the filtration direction to obtain the sample for microstructure observation at filter and melt
8 interface. Samples for metallographic examination were prepared by a standard technique. Field-emission
9 scanning electron microscopy (FE-SEM, SUPRA 35VP, Carl-Zeiss Company) equipped with an energy
10 dispersive X-ray spectroscopy (EDS) was used for microstructure analysis.
11
12
13

14 RESULTS AND DISCUSSION

15
16 Fig. 1 shows the yield strength and elongation of the A380 alloy HPDC tensile samples after rotary
17 degassing and high shear melt conditioning. The distribution range of yield strength and elongation of A380
18 alloy with rotary degassing was from 129.1MPa to 152.9MPa, and from 2.91% to 6.88% respectively. With
19 application of high shear melt conditioning, the distribution range of yield strength and elongation was from
20 130.7MPa to 149.9MPa, and from 3.73% to 6.62% respectively.
21
22
23

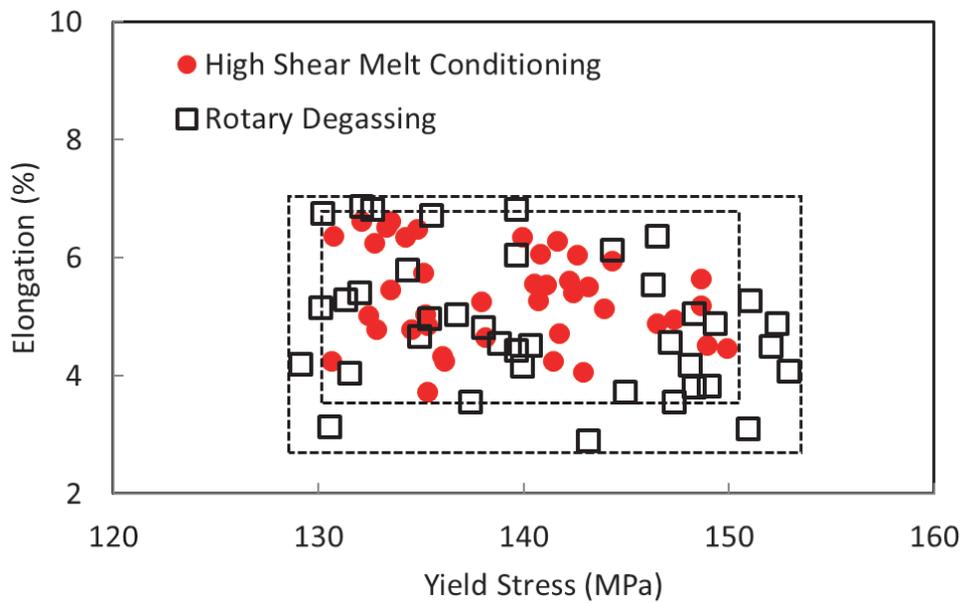

45 Fig.1. The comparison of mechanical properties of A380 alloys between rotary degassing and high shear
46 melt conditioning showed that melt treatment with high shear can improve the variation both on yield
47 strength and elongation
48
49

50 It can be seen from the comparison that high shear melt conditioning can reduce the variation of both
51 yield strength and elongation. To obtain the coefficient of variation (CV), the equation of $CV=SD/\mu*100\%$
52 is used, in which SD is standard deviation and μ is the average value of yield strength or elongation. The
53 small value of CV means the narrow distribution range of properties and the good property stability. The
54
55
56
57
58
59
60
61
62
63
64
65

influence of high shearing melt conditioning on the coefficient of variation of A380 alloy was shown in table 1. The data in table 1 revealed that with high shearing treatment, yield strength variation was decreased from 5.48% to 3.62%, and elongation variation was decreased from 21.83% to 13.96%. The variation comparison indicated that high shear melt conditioning can improve the mechanical properties variation.

Table 1. Coefficient of variation of yield strength and elongation of A380 alloys with melt treatment of rotary degassing and high shear respectively

Melt treatment	Average value (μ)		Standard Deviation (SD)		Coefficient of Variation(CV)	
	Yield strength (MPa)	Elongation (%)	Yield strength (MPa)	Elongation (%)	Yield strength (%)	Elongation (%)
Rotary degassing	141.10	4.90	7.74	1.06	5.48	21.83
HSMC	139.30	5.40	5.04	0.75	3.62	13.96

To investigate the mechanism of variation improvement, observation of microstructure evolution was necessary to reveal the grain refinement performance, secondary phase distribution and porosity distribution and so on. Fig. 2 shows the grain morphology of α -Al formed in the shot sleeve (α -Al₁) and in the die cavity (α -Al₂) of A380 alloy with rotary degassing (Fig. 2a) and with high shear melt conditioning (Fig. 2b). α -Al₁ grains formed in shot sleeve are normally coarse due to the relative slow cooling rate and more growth time after nucleation and α -Al₂ grains formed in die cavity are finer because of the high cooling rate. With rotary degassing the size of the coarse α -Al₁ grains was about 50 μ m, and the size of α -Al₂ grains was about 10 μ m. After application of high shear melt conditioning, both the size of coarse α -Al₁ grains and fine α -Al₂ grains was reduced to about 30 μ m for α -Al₁ grains and 5 μ m for α -Al₂ grains. More importantly, the size distribution of α -Al grains was more uniform than that of microstructure without high shear application.


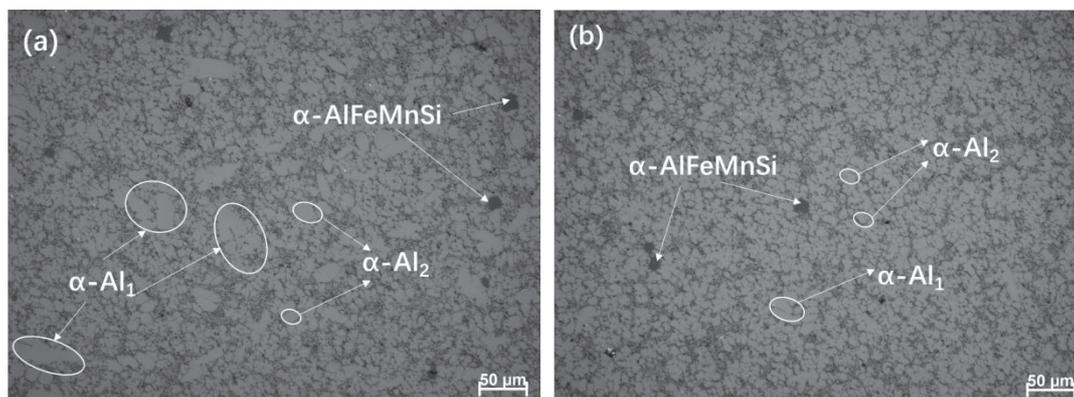


Fig. 2. Grain morphology of A380 alloys showed that better grain refinement and uniform grain distribution were achieved with high shear melt conditioning (b) compared to the microstructure without high shearing (a), and the size of α -Al formed in shot sleeve (α -Al₁) was decreased significantly with high shearing

1 The refinement of α -Al both formed in shot sleeve and die cavity illustrated that high shear melt
2 conditioning can promote the nucleation performance of A380 alloy. Spinel (MgAl_2O_4) was revealed that it
3 can be the effective nucleation site for α -Al in Al-Mg alloy [7, 13] and in Al alloy [8, 15] due to the small
4 misfit of about 1.4% between spinel and Al. Basing on the relationship between undercooling and nuclei size,
5 to activate the spinel as effective nuclei, the size distribution of particles became the important factor to
6 dominant the spinel performance on grain refinement of Al alloy produced by HPDC processing.
7

8
9 The particles in A380 alloys were analyzed using SEM after collecting via Prefil[®]-Footprinter and the
10 results were shown in fig.3. It can be seen from fig. 3a that TiB_2 was the main particle type in A380 alloy
11 with rotary degassing, and its size was about or more than $1\mu\text{m}$. These TiB_2 particles were from the retained
12 TiB_2 particles added as refiner in recycled Al. Fig. 3b showed that besides TiB_2 particles, MgAl_2O_4 with two
13 kinds of size distribution were found in A380 alloy with high shear melt conditioning. The size of relative
14 big MgAl_2O_4 particles was about 300nm, and the size of small particles was about 80nm. The existence of
15 MgAl_2O_4 indicated that high shear can promote the formation of such phases. The formation mechanism of
16 MgAl_2O_4 can attributed to the disperse effect of high shear on existing Al_2O_3 film in Al melt. There always
17 have many Al_2O_3 film in melt due to the disturbance of melt surface and the active reaction between Al and
18 O_2 . During high shear unit running, the melt was forced into the shearing area with a shear rate of about 10^5 -
19 10^6 s^{-1} and any oxide films into these area would be breakup into fine particles. If the melt contains Mg, the
20 reaction between dispersed Al_2O_3 particles and Mg would occur and then form MgAl_2O_4 .
21
22
23
24
25
26

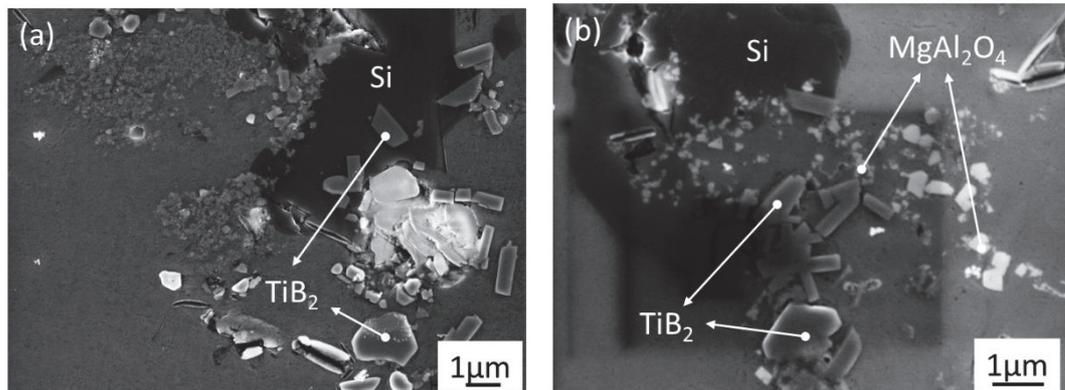

41 Fig. 3. Microstructure of prefil samples showed that TiB_2 was the main type of particles in A380 alloy with
42 rotary degassing (Fig.3a), and MgAl_2O_4 and TiB_2 were the main kinds of particles in A380 alloy with high
43 shear melt conditioning (Fig.3b)
44
45
46

47 CONCLUSIONS

48 High shear melt conditioning can reduce the variation of yield strength and elongation of HPDC A380
49 alloy. With MC-HPDC, the coefficient of variation of elongation was decreased from 21.8% to 13.9%, and
50 yield strength variation coefficient was reduced from 5.5% to 3.6%. The improved property variation is
51 attributed to enhanced nucleation both in shot sleeve and the die cavity caused by formation of MgAl_2O_4
52 particles, in which double size distribution of about 80nm and 300nm were synthesized. The grain refinement
53
54
55
56
57
58
59
60
61
62
63
64
65

1 principle was ascribed to the good orientation relationship and small misfit between α -Al and MgAl₂O₄.
2
3

4 ACKNOWLEDGMENTS

5

6 This project is financially supported by EPSRC UK in the EPSRC Centre for Innovative Manufacturing in
7 Liquid Metal Engineering (The EPSRC Centre—LiME).
8
9

10 REFERENCES

- 11
12
13 [1] A. Fabrizi, S. Ferraro, G. Timelli, *Mater. Charact.*, 85, 13 (2013).
14 [2] H. Yang, S. Ji, Z. Fan, *Mater. Des.*, 85, 823 (2015).
15 [3] S. Seifeddine, I.L. Svensson, *Metall. Sci. Technol.*, 27, 11 (2009).
16 [4] X. Li, S.M. Xiong, Z. Guo, *J. Mater. Process. Technol.*, 231, 1 (2016).
17 [5] B.H. Hu, K.K. Tong, X.P. Niu, I. Pinwill, *J. Mater. Process. Technol.*, 105, 128 (2000).
18 [6] D.R. Gunasegaram, M. Givord, R.G. O'Donnell, B.R. Finnin, *Mater. Sci. Eng. A.*, 559, 276 (2013).
19 [7] S.L. dos Santos, R.A. Antunes, S.F. Santos, *Mater. Des.*, 88, 1071 (2015).
20 [8] T.E. Qested, A.T. Dinsdale, A.L. Greer, *Acta Mater.*, 53, 1323 (2005).
21 [9] T.E. Qested, A.L. Greer, *Acta Mater.*, 52, 3859 (2004).
22 [10] M.A. Easton, D.H. Stjohn, *Acta Mater.*, 49, 1867 (2001).
23 [11] Z. Fan, Y. Wang, M. Xia, S. Arumuganathar, *Acta Mater.*, 57, 4891 (2009).
24 [12] H.T. Li, M. Xia, P. Jarry, G.M. Scamans, Z. Fan, *J. Cryst. Growth.*, 314, 285 (2011).
25 [13] H.T. Li, Y. Wang, Z. Fan, *Acta Mater.*, 60, 1528 (2012).
26 [14] R. Haghayeghi, E.J. Zoqui, D.G. Eskin, H. Bahai, *J. Alloys Compd.*, 485, 807 (2009).
27 [15] D. Zhang, L. Wang, M. Xia, N. Hari Babu, J.G. Li, *Mater. Charact.*, 119, 92 (2016)
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65